

University of Texas at Tyler

Scholar Works at UT Tyler

Health and Kinesiology Faculty Publications
and Presentations

Department of Health and Kinesiology

Spring 5-30-2022

Antibacterial and Antifungal Activity of Functionalized Cotton Fabric with Nanocomposite Based on Silver Nanoparticles and Carboxymethyl Chitosan

Carlos Alberto Arenas-Chavez

Luciana Maria de Hollanda

Arturo A. Arce-Esquivel
University of Texas at Tyler, aarce@uttyler.edu

Aldo Alvarez-Risco

Shyla Del-Aguila-Arcentales

See next page for additional authors

Follow this and additional works at: https://scholarworks.uttyler.edu/hkdept_fac



Part of the [Kinesiology Commons](#)

Recommended Citation

Arenas-Chavez, Carlos Alberto; de Hollanda, Luciana Maria; Arce-Esquivel, Arturo A.; Alvarez-Risco, Aldo; Del-Aguila-Arcentales, Shyla; Yanez, Jamie A.; and Vera-Gonzales, Corina, "Antibacterial and Antifungal Activity of Functionalized Cotton Fabric with Nanocomposite Based on Silver Nanoparticles and Carboxymethyl Chitosan" (2022). *Health and Kinesiology Faculty Publications and Presentations*. Paper 23.

<http://hdl.handle.net/10950/4335>

This Article is brought to you for free and open access by the Department of Health and Kinesiology at Scholar Works at UT Tyler. It has been accepted for inclusion in Health and Kinesiology Faculty Publications and Presentations by an authorized administrator of Scholar Works at UT Tyler. For more information, please contact tgullings@uttyler.edu.

Author

Carlos Alberto Arenas-Chavez, Luciana Maria de Hollanda, Arturo A. Arce-Esquivel, Aldo Alvarez-Risco, Shyla Del-Aguila-Arcentales, Jamie A. Yanez, and Corina Vera-Gonzales

Article

Antibacterial and Antifungal Activity of Functionalized Cotton Fabric with Nanocomposite Based on Silver Nanoparticles and Carboxymethyl Chitosan

Carlos Alberto Arenas-Chávez ¹, Luciana Maria de Hollanda ², Arturo A. Arce-Esquivel ³, Aldo Alvarez-Risco ⁴, Shyla Del-Aguila-Arcentales ⁵, Jaime A. Yáñez ^{6,7,*} and Corina Vera-Gonzales ^{8,9}

- ¹ Departamento Académico de Biología, Universidad Nacional de San Agustín de Arequipa, Arequipa 04000, Peru; carenasc@unsa.edu.pe
- ² Centro Universitário Metrocamp, Wyden University, Campinas, São Paulo 13035-350, Brazil; luciana.hollanda@professores.unimetrocamp.edu.br
- ³ Department of Health and Kinesiology, School of Community and Rural Health, The University of Texas, Tyler, TX 75799, USA; aarce@uttyler.edu
- ⁴ Facultad de Ciencias Empresariales y Económicas, Carrera de Negocios Internacionales, Universidad de Lima, Lima 15023, Peru; aralvare@ulima.edu.pe
- ⁵ Escuela Nacional de Marina Mercante “Almirante Miguel Grau”, Callao 07021, Peru; sdelaguila@enammm.edu.pe
- ⁶ Vicerrectorado de Investigación, Universidad Norbert Wiener, Lima 15046, Peru
- ⁷ Gerencia Corporativa de Asuntos Científicos y Regulatorios, Teoma Global, Lima 15073, Peru
- ⁸ Departamento Académico de Química, Universidad Nacional de San Agustín de Arequipa, Arequipa 04000, Peru; cverag@unsa.edu.pe
- ⁹ Laboratorio de Preparación, Caracterización e Identificación de Nanomateriales (LAPCI NANO), Universidad Nacional de San Agustín de Arequipa, Arequipa 04000, Peru
- * Correspondence: jaime.yanez@uwiener.edu.pe



Citation: Arenas-Chávez, C.A.; de Hollanda, L.M.; Arce-Esquivel, A.A.; Alvarez-Risco, A.; Del-Aguila-Arcentales, S.; Yáñez, J.A.; Vera-Gonzales, C. Antibacterial and Antifungal Activity of Functionalized Cotton Fabric with Nanocomposite Based on Silver Nanoparticles and Carboxymethyl Chitosan. *Processes* **2022**, *10*, 1088. <https://doi.org/10.3390/pr10061088>

Academic Editor: Blaž Likozar

Received: 23 April 2022

Accepted: 24 May 2022

Published: 30 May 2022

Publisher's Note: MDPI stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.



Copyright: © 2022 by the authors. Licensee MDPI, Basel, Switzerland. This article is an open access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

Abstract: Cotton is the most widely used natural fiber for textiles; however, the capacity of cotton fibers to absorb large amounts of moisture, retain oxygen, and have a high specific surface area makes them more prone to microbial contamination, becoming an appropriate medium for the growth of bacteria and fungi. In recent years, the incorporation of silver nanoparticles in textile products has been widely used due to their broad-spectrum antibacterial activity and low toxicity towards mammalian cells. The aim of the current study is to continue the assessment of our developed nanocomposite and evaluate the antibacterial and antifungal activity of the nanocomposite based on silver nanoparticles and carboxymethyl chitosan (AgNPs-CMC) against *Escherichia coli*, *Staphylococcus aureus*, and *Candida albicans*, evaluated by the well diffusion method. The antibacterial activity against *E. coli* and *S. aureus* was also evaluated by the qualitative method of inhibition zone and the quantitative method of colony counting. Likewise, the antifungal activity of the functionalized fabric against *Candida albicans* and *Aspergillus niger* was determined by the inhibition zone method and the antifungal activity method GBT 24346-2009, respectively. The functionalized fabric showed 100% antibacterial activity against *E. coli* and *S. aureus* and good antifungal activity against *C. albicans* and *A. niger*. Our results indicate that the functionalized fabric could be used in garments for hospital use to reduce nosocomial infections.

Keywords: nanocomposite; functionalized fabric; antimicrobial; antifungal; cotton

1. Introduction

Cotton is the most widely used natural fiber for textiles due to its softness, low price, easy mass production, and it is particularly suitable for manufacturing medical products, healthcare products, and hygiene [1–3]. However, cotton fibers absorb large amounts of moisture [4], retain oxygen, and have a high specific surface area [5]. This also makes them more prone to microbial contamination, becoming an appropriate medium for the

growth of bacteria and fungi [6]. In this sense, cotton fibers with antimicrobial properties have attracted considerable attention due to their potential application in several fields such as health and medicine [7–13]. The use of biocides such as triclosan [14], quaternary ammonium compounds [15], or organosilicons [16,17] has been reported. However, these antimicrobial agents often produce highly toxic or undesirable by-products [18–20]. In recent years, nanocarrier systems have been widely used in various fields including nutraceuticals [21–31], pharmaceuticals [32–35], which could affect biodisposition [36–60], lymphatic transport [61], ophthalmic drug delivery [62], and toxicity [63–67]. The incorporation of silver nanoparticles in textile products has been widely used due to their broad-spectrum antibacterial activity and low toxicity towards mammalian cells [68–75]. The antimicrobial properties of silver nanoparticles are size-dependent because silver nanoparticles of different sizes have different surface/volume ratios, producing different antibacterial efficiency during their interaction with microorganisms [76–81]. The instability of silver nanoparticles has been reported because a variation in the size of the nanoparticles when they are applied directly on textiles can cause agglomeration of the nanoparticles, resulting in a decrease in the antimicrobial effect [82–85].

It has been described that the use of stabilizing agents, such as natural polymers, to form nanocomposites significantly improves the stability of the nanoparticles [86,87]. Polymer-based inorganic nanocomposites combine organic, inorganic, and nanomaterial compounds' unique mechanical, optical, and electrical properties. The polymer chains of these nanocomposites can contain reactive groups. In combination with the inorganic antimicrobial agents, they have exceptional advantages such as exhibiting synergistic antimicrobial effects, improving the adhesion to the substrates, avoiding agglomeration, and improving the stability of silver nanoparticles inside the polymer matrix [5,88]. There is only one study that used carboxymethyl chitosan to pad cotton fabric and then soak it in silver nitrate and black rice extract [89]. However, carboxymethyl cellulose has been preferably used as a reductant agent [90]. Other studies report the use of various reductant and stabilizing agents for silver nanoparticles such as acacia gum [91], a bionic mussel-like material named polydopamine (PDA) [74], ethanolamine [92], and carrageenan [93]. Furthermore, recently, a tri-component nanoparticle of silver, copper, and zinc oxide has been developed using polymethylol compound (PMC) or functionalized polyethyleneimine (FPEI) polymers as both reductant and stabilizing agents [94]. Other approaches have been implemented to improve properties of nanocomposites such as enhancing thermoelectric performance by realigning Fermi level [95], development of polyaniline derivatives towards multistimulus responsiveness by plasma activation [96], plasma treatment toward electrically conductive and superhydrophobic cotton fibers using polypyrrole [97], and self-cleanable cotton fibers using silver carbamate and plasma activation [98].

The novelty of our manuscript is centered around the assessment of antibacterial and antifungal activity of the nanocomposite previously synthesized and characterized by our research group based on silver nanoparticles and carboxymethyl chitosan (AgNPs-CMC) [99]. The nanocomposite obtained from the complex $[\text{Ag}(\text{NH}_3)_2]^+$ was synthesized under the same conditions as AgNO_3 , but at a basic pH. UV-VIS spectrophotometry verified the plasmon formation of silver nanoparticles at 410 nm for both silver sources [99]. Our results by Dynamic Light Dispersion (DLS) for AgNO_3 , showed a monodisperse distribution of the nanocomposite with an average hydrodynamic size of 166.7 nm [99]. Infrared spectroscopy measurements with Fourier Transform (FT-IR) showed the inhibition of the spectral bands at 879 and 723 cm^{-1} indicating the presence of AgNPs in the nanocomposite AgNPs-CMC [99]. The results of scanning electron microscopy (SEM-STEM) showed that the silver nanoparticles in the nanocomposite were spherical in shape and of a size of 5 to 20 nm [99]. The aim of the current study is to continue the assessment of our developed nanocomposite and evaluate its antibacterial and antifungal activity against *E. coli*, *S. aureus*, and *C. albicans* was evaluated by the well diffusion method. The antibacterial activity against *E. coli* and *S. aureus* was also evaluated by the qualitative method of inhibition zone and the quantitative method of colony counting.

The materials and methods are presented in Section 2. Section 3 provides the outcomes and discussion. Conclusions are described in Section 4.

2. Materials and Methods

2.1. Reagents and Materials

The following reagents were used: potassium dihydrogen phosphate ($\text{pa} \geq 99\%$) (Merck Millipore, Saint Louis, MO, USA), sodium hydroxide ($\text{pa} \geq 99\%$) (Merck Millipore, Saint Louis, MO, USA), trypticase soy agar (TSA) (Liofilchem, Abruzzi, Italy), Trypticase soy broth (TSB) (Liofilchem, Abruzzi, Italy), *Escherichia coli* (ATCC 25922) (Merck Millipore, Saint Louis, MO, USA), *Staphylococcus aureus* (ATCC 25923) (Merck Millipore, Saint Louis, MO, USA). *Candida albicans* and *Aspergillus niger* were provided by the Microbiology Laboratory of the Universidad Nacional de San Agustín (UNSA). The nanocomposite material (AgNPs-CMC) was provided by the Laboratory of Preparation, Characterization and Identification (LAPCL_NANO) of the Universidad Nacional de San Agustín de Arequipa (UNSA).

2.2. Synthesis of Nanocomposite, Preparation and Functionalization of Cotton Fabric

We have previously described the synthesis of the silver nanoparticles and carboxymethyl chitosan (AgNPs-CMC) [99]. Briefly, the nanocomposite synthesis was performed using 20 mL of silver nitrate solution (1 mM) with the dropwise addition of 30 mL O-CMC (0.025%) with constant stirring (700 rpm) for 30 min at 90 °C. The fabric was washed with a non-ionic detergent (2.0 g/L concentration) at 90 °C with constant stirring (30 rpm) for 15 min. Then, it was rinsed twice with distilled water at 60 °C with constant stirring (30 rpm) for 10 min in an Eco Dyer. One portion was kept at this point as control fabric, and the other portion was ready for functionalization. The fabric was dried at room temperature for 24 h. The fabric was functionalized using the exhaustion method [100] in an Eco Dyer. For this, one gram of fabric was submerged in 20 mL of an AgNPs-CMC nanocomposite solution under the following conditions: 90 °C temperature, constant stirring (30 rpm), liquor ratio of 1:20, and for 15 min. Then, the fabric was rinsed twice with distilled water at 30 °C temperature, constant stirring (30 rpm), liquor ratio of 1:20 for 15 min using the Eco Dyer. Finally, the fabric was dried at 80 °C for 15 min.

2.3. Antibacterial Activity of the Nanocomposite

The antibacterial activity was evaluated by the standard well diffusion method. Inoculation of the bacteria *E. coli* (ATCC 25922) and *S. aureus* (ATCC 25923) were prepared at a concentration of 1.02×10^3 CFU/mL and 1.36×10^4 CFU/mL, respectively. Then, 20 μL of the inoculum was measured and plated uniformly on the surface of the Mueller Hinton agar (MH). Then, 3 wells of 7 mm in diameter were made, distributed equidistantly in the Petri dish, and 20 μL of the nanocomposite was placed (AgNPs-CMC). The plates were then incubated for 24 h at 37 °C; then, the inhibition zone was measured around the well using a vernier caliper [101].

2.4. Antibacterial Activity of Cotton Fabric Functionalized with the Nanocomposite

2.4.1. Inhibition Zone Method

The antibacterial activity was evaluated by the qualitative zone inhibition method. Initially, inoculation of the bacteria *E. coli* (ATCC 25922) and *S. aureus* (ATCC 25923) was prepared at a concentration of 1.02×10^3 CFU/mL and 1.36×10^4 CFU/mL, respectively. Then, 20 μL of the inoculum was measured and plated uniformly in Petri dishes with Mueller–Hinton agar (MH) and allowed to dry for 10 min. On the agar surface, disks (previously sterilized by UV) of the control and functionalized fabric of 0.8 cm diameter were placed. The plates were then incubated for 24 h at 37 °C; then, the inhibition zone was measured around the fabric using a vernier caliper [102].

2.4.2. Colony Counting Method

The antibacterial effect of the fabric functionalized with nanocomposite AgNPs-CMC was tested using the standard quantitative method ASTM E-2149-10 against *E. coli* and *S. aureus*. Then, a fabric sample, weighing 1000 ± 0.001 g, was cut into small pieces with a size of about 1×1 cm², which were sterilized by UV radiation for 30 min. Then, these fabric pieces were immersed in a 250 mL bottle with 50 mL of 0.3 mM dihydrogen phosphate buffer solution, pH = 7.2 containing 1.5 to 3.0×10^5 CFU/mL of bacteria. The bottle was shaken at 150 rpm in a shaker at 37 °C, for 1 h. From each incubated sample, 1 mL of solution was taken and diluted to 10^{-1} , 10^{-2} , and 10^{-3} and then seeded on an agar plate. All plates were incubated at 37 °C for 24 h, and the colonies formed were counted with the naked eye. The percentage of bacterial reduction was determined as follows:

$$\text{Bacterial reduction in CFU (\%)} = x = \frac{B - A}{B} \times 100$$

where:

A = Colony-forming units (CFU)/mL for the bottle at the end time, after one hour of contact;
B = Colony-forming units (CFU)/mL for the bottle at time zero, after one minute of contact.

2.5. Antifungal Activity of the Nanocomposite

The antifungal activity of the nanocomposite was evaluated by the standard well diffusion method. An inoculum of *C. albicans* (ATCC 10231) was prepared at a 1.06×10^7 CFU/mL concentration. Then, 20 µL of the inoculum was measured and plated uniformly on the potato dextrose agar (PDA) surface. Then, 3 wells of 7 mm diameter were made equidistantly distributed in the petri dish, where 20 µL of the nanocomposite (AgNPs-CMC) was placed. The plates were then incubated for 24 h at 37 °C, after which time the zone of inhibition was measured around the well using a vernier caliper [101].

2.6. Antifungal Activity of Cotton Fabric Functionalized with the Nanocomposite

Antifungal activity was evaluated by the qualitative zone inhibition method. An inoculum of *C. albicans* of 1.06×10^7 CFU/mL was initially prepared. It was seeded in a PDA medium and then proceeded in the same way as in the case of *E. coli* and *S. aureus* described above.

2.7. Antifungal Activity of the Cotton Fabric Functionalized with the Nanocomposite against a Filamentous Fungus

The antifungal activity of the control cotton fabric and the functionalized fabric was evaluated against an isolated strain of *A. niger* according to the standard method of antifungal activity GBT 24346-2009 [103].

2.8. Statistical Analysis

Statistical analysis was performed by Student's *t* test using STATA Statistical Software: Release 15 (StataCorp LLC, College Station, TX, USA). A value of $p < 0.05$ (*) was considered to be statistically significant. All the studies were performed in triplicates.

3. Results and Discussion

3.1. Antibacterial Activity of the Nanocomposite

Figure 1 shows the inhibition of antibacterial activity by the well diffusion method against *E. coli* and *S. aureus*. There is an average inhibition halo of 5 mm for *E. coli* and 8 mm for *S. aureus*. The control exhibited no inhibition halo for *E. coli* and *S. aureus*. These results show that the nanocomposite has excellent antibacterial activity against these two types of Gram-negative and Gram-positive bacteria, respectively.

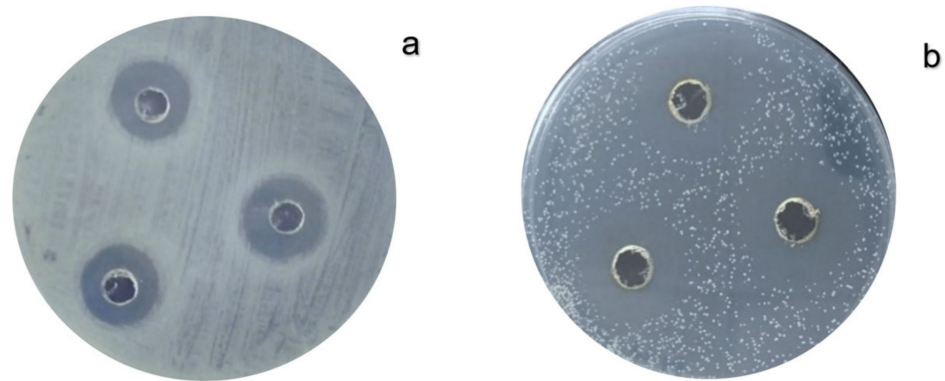


Figure 1. Antibacterial activity of the nanocomposite AgNPs-CMC against *E. coli* (a) and *S. aureus* (b).

3.2. Antibacterial Activity of the Cotton Fabric Functionalized with the Nanocomposite

The antibacterial activity of the fabric functionalized with the nanocomposite AgNPs-CMC was evaluated qualitatively by the zone of inhibition method and quantitatively by the colony counting method, according to the ASTM E-2149-10 technical standard. Figure 2 shows the antibacterial activity of the control and textile fabric functionalized with the nanocomposite. The textile functionalized with nanocomposite shows an average zone of inhibition of 1.5 mm and 2 mm around the textile for *E. coli* and *S. aureus*, respectively, which indicates that the textile functionalized with the nanocomposite possesses an antibacterial activity due to the action of the nanocomposite on the bacterial cells. The results in Table 1 and Figure 3 showed a bacterial reduction of 0% in the control fabric against *E. coli* and *S. aureus*. In contrast, the functionalized fabric exhibited a 100% bacterial reduction in both bacterial strains, showing the excellent antibacterial activity of the functionalized fabric compared to the control.

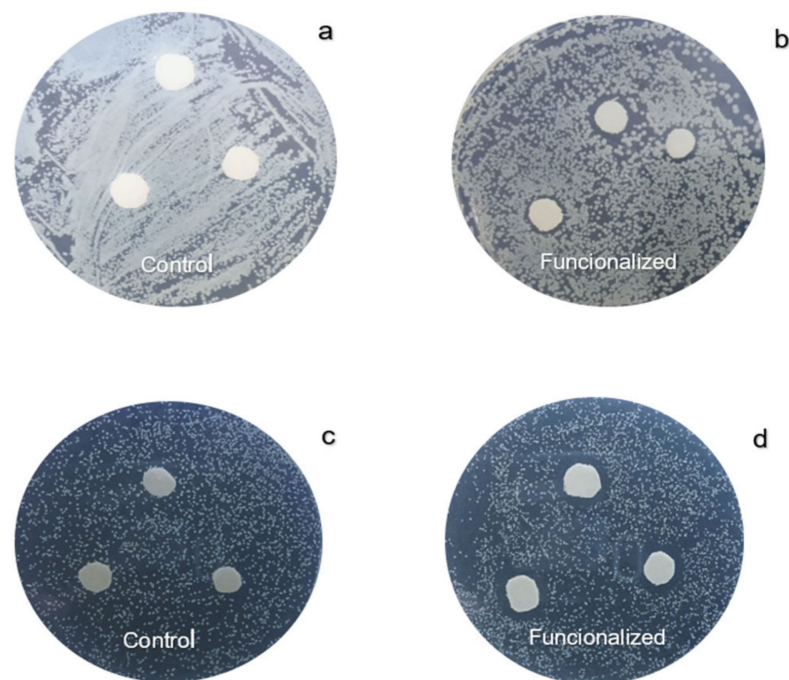


Figure 2. Antibacterial activity of the control and functionalized fabric against *E. coli* (a,b) and *S. aureus* (c,d).

Table 1. Antibacterial reduction of control fabric and fabric functionalized with nanocomposite AgNPs-CMC. Results expressed as mean \pm standard deviation ($n = 3$).

Sample	Antibacterial Activity			
	<i>E. coli</i>		<i>S. aureus</i>	
	Bacteria UFC/mL	% reduction	Bacteria UFC/mL	% reduction
Control	107500 \pm 13527	No reduction	73167 \pm 2631	No reduction
Functionalized	0 \pm 0 *	100%	0 \pm 0 *	100%

* $p < 0.05$.

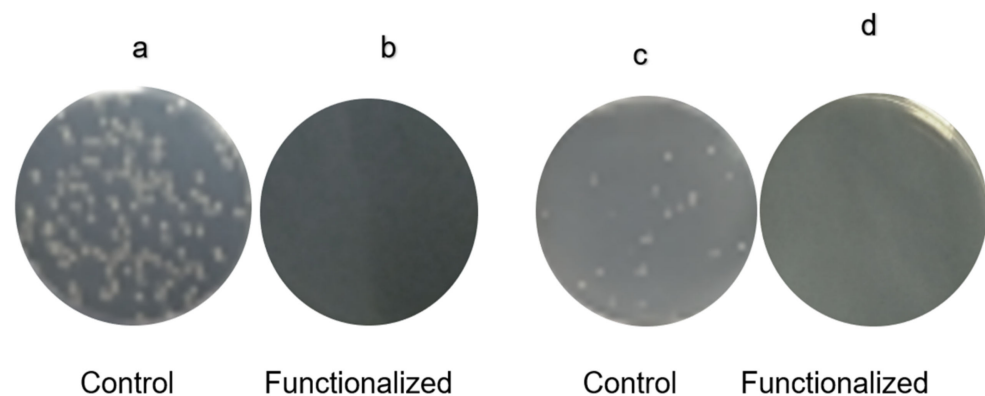


Figure 3. Antibacterial activity of the control and functionalized fabric against *E. coli* (a,b) and *S. aureus* (c,d).

Our antibacterial activity results are superior to those reported previously, with 80–90% bacterial reduction [57,68,93,94]. Similarly, these results for bacterial reduction correlate with Paszkiewicz et al. [104], where they used bimetallic silver and copper nanoparticles. The bactericidal mechanism of the silver nanoparticles is only partially known, and the antibacterial effect reported for the functionalized fabric could be explained based on the following mechanisms: the Ag⁺ ions formed from the oxidation of zero-valent silver (Ag⁰) interact with the sulfur of the proteins present in the bacterial cell membrane or intracellularly, which affects the viability of the bacterial cell. It has also been proposed that the silver/silver ion (AgNPs/Ag⁺) nanoparticles can act with the molecules of phosphorus present in DNA, producing an inactivation of DNA replication [105–109].

The release of Ag⁺ from the AgNPs can also catalyze the production of oxygen radicals that oxidize the molecular structure of the bacteria. This mechanism does not require direct contact between the antimicrobial agent Ag⁺ and the bacterium because the active oxygen produced diffuses from the textile to the surrounding environment [105,109].

3.3. Antifungal Activity of the Nanocomposite

Figure 4 shows the inhibition of antifungal activity by the well diffusion method against *C. albicans*. An average inhibition halo of 1.5 mm was observed exhibiting that the nanocomposite has antifungal activity against *C. albicans*. The control exhibited no inhibition halo for *C. albicans*.

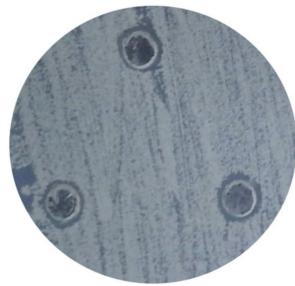


Figure 4. Antifungal activity of nanocomposite AgNPs-CMC against *C. albicans*.

3.4. Antifungal Activity of the Cotton Fabric Functionalized with the Nanocomposite

Figure 5 shows the antifungal activity of the control and textile fabric functionalized with the nanocomposite. The functionalized fabric shows an average zone of inhibition of 2 mm against *C. albicans*, which indicates that the fabric functionalized with the nanocomposite possesses antifungal activity. The antifungal activity of the control cotton and the functionalized fabric was evaluated against an isolated strain of *Aspergillus niger* according to the standard method GBT 24346-2009 [103,110]. Figure 6 shows the results of the antifungal activity of the control cotton and functionalized fabric with the nanocomposite.

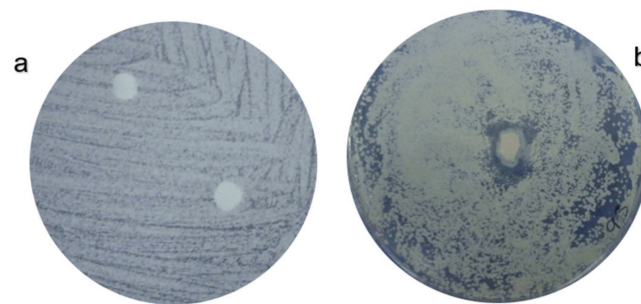


Figure 5. Antifungal activity of control (a) and functionalized (b) fabric against *C. albicans*.

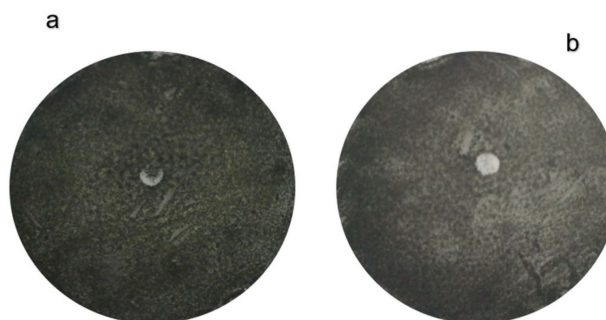


Figure 6. Antifungal activity of control (a) and functionalized (b) fabric against *A. niger*.

The control fabric (Figure 6a) is covered by the filamentous fungus, indicating that this fabric does not show resistance to the growth of *A. niger*. However, the textile functionalized with the nanocomposite (Figure 6b) presents a greater surface area without the growth of the fungus.

Gao et al. reported similar results, with the difference that they worked with a functionalized fabric with a nanocomposite based on P(DMDAAC-AGE)/Ag/ZnO, which presented an ability to inhibit the growth of *A. flavus* up to 5 days [103]. However, our functionalized textile showed a growth inhibition for up to 7 days, which shows a better antifungal effect.

4. Conclusions

Cotton is the most widely used natural fiber for textiles, with the recent incorporation of silver nanoparticles due to its broad-spectrum antibacterial activity and low toxicity towards mammalian cells. This work reported 100% antibacterial activity against *E. coli* and *S. aureus* and good antifungal activity against *C. albicans* and *A. niger* of our functionalized fabric with the nanocomposite based on silver nanoparticles and carboxymethyl chitosan (AgNPs-CMC). This functionalized fabric showed that our fabric could be used in garments for hospital use to reduce nosocomial infections, which invites further investigation and assessment of other applications in a larger number of microorganisms involved in nosocomial infections.

Author Contributions: Conceptualization, C.A.A.-C., L.M.d.H. and C.V.-G.; methodology, C.A.A.-C., L.M.d.H. and C.V.-G.; software, C.A.A.-C., L.M.d.H. and C.V.-G.; validation, C.A.A.-C., L.M.d.H. and C.V.-G.; formal analysis, C.A.A.-C., L.M.d.H. and C.V.-G.; investigation, C.A.A.-C., L.M.d.H. and C.V.-G.; resources, C.A.A.-C., L.M.d.H. and C.V.-G.; data curation, C.A.A.-C., L.M.d.H. and C.V.-G.; writing—original draft preparation, C.A.A.-C., L.M.d.H., C.V.-G., A.A.-R., S.D.-A.-A. and J.A.Y.; writing—review and editing, C.A.A.-C., L.M.d.H., C.V.-G., A.A.A.-E., A.A.-R., S.D.-A.-A. and J.A.Y.; visualization, C.A.A.-C., L.M.d.H., C.V.-G., A.A.A.-E., A.A.-R., S.D.-A.-A. and J.A.Y. All authors have read and agreed to the published version of the manuscript.

Funding: This research received no external funding.

Data Availability Statement: The data presented in this study are available on request from the corresponding author

Conflicts of Interest: The authors declare no conflict of interest.

References

1. Hebeish, A.; Hashem, M.; El-Hady, M.M.A.; Sharaf, S. Development of CMC hydrogels loaded with silver nano-particles for medical applications. *Carbohydr. Polym.* **2013**, *92*, 407–413. [[CrossRef](#)] [[PubMed](#)]
2. Shahid, M.; Mohammad, F. Green Chemistry Approaches to Develop Antimicrobial Textiles Based on Sustainable Biopolymers—A Review. *Ind. Eng. Chem. Res.* **2013**, *52*, 5245–5260. [[CrossRef](#)]
3. Kamble, Z.; Behera, B.K. Mechanical properties and water absorption characteristics of composites reinforced with cotton fibres recovered from textile waste. *J. Eng. Fibers Fabr.* **2020**, *15*, 1558925020901530. [[CrossRef](#)]
4. Mao, Z.; Yu, H.; Wang, Y.; Zhang, L.; Zhong, Y.; Xu, H. States of Water and Pore Size Distribution of Cotton Fibers with Different Moisture Ratios. *Ind. Eng. Chem. Res.* **2014**, *53*, 8927–8934. [[CrossRef](#)]
5. Yuan, G.; Cranston, R. Recent Advances in Antimicrobial Treatments of Textiles. *Text. Res. J.* **2008**, *78*, 60–72. [[CrossRef](#)]
6. Cheung, H.-Y.; Ho, M.-P.; Lau, K.-T.; Cardona, F.; Hui, D. Natural fibre-reinforced composites for bioengineering and environmental engineering applications. *Compos. Part B: Eng.* **2009**, *40*, 655–663. [[CrossRef](#)]
7. Moritz, M.; Geszke-Moritz, M. The newest achievements in synthesis, immobilization and practical applications of antibacterial nanoparticles. *Chem. Eng. J.* **2013**, *228*, 596–613. [[CrossRef](#)]
8. Zhang, Y.; Xu, Q.; Fu, F.; Liu, X. Durable antimicrobial cotton textiles modified with inorganic nanoparticles. *Cellulose* **2016**, *23*, 2791–2808. [[CrossRef](#)]
9. Fang, F.; Chen, X.; Zhang, X.; Cheng, C.; Xiao, D.; Meng, Y.; Ding, X.; Zhang, H.; Tian, X. Environmentally friendly assembly multilayer coating for flame retardant and antimicrobial cotton fabric. *Prog. Org. Coat.* **2016**, *90*, 258–266. [[CrossRef](#)]
10. Zhang, T.; Yu, H.; Li, J.; Song, H.; Wang, S.; Zhang, Z.; Chen, S. Green light-triggered antimicrobial cotton fabric for wastewater disinfection. *Mater. Today Phys.* **2020**, *15*, 100254. [[CrossRef](#)]
11. Li, S.; Lin, X.; Liu, Y.; Li, R.; Ren, X.; Huang, T.-S. Phosphorus-nitrogen-silicon-based assembly multilayer coating for the preparation of flame retardant and antimicrobial cotton fabric. *Cellulose* **2019**, *26*, 4213–4223. [[CrossRef](#)]
12. Granados, A.; Pleixats, R.; Vallribera, A. Recent Advances on Antimicrobial and Anti-Inflammatory Cotton Fabrics Containing Nanostructures. *Molecules* **2021**, *26*, 3008. [[CrossRef](#)]
13. Gao, F.; Mi, Y.; Wu, X.; Yao, J.; Qi, Q.; Chen, W.; Cao, Z. Preparation of quaternized chitosan/Ag composite nanogels in inverse miniemulsions for durable and antimicrobial cotton fabrics. *Carbohydr. Polym.* **2022**, *278*, 118935. [[CrossRef](#)]
14. Orhan, M. Triclosan applications for biocidal functionalization of polyester and cotton surfaces. *J. Eng. Fibers Fabr.* **2020**, *15*, 1558925020940104. [[CrossRef](#)]
15. Zhang, S.; Yang, X.; Tang, B.; Yuan, L.; Wang, K.; Liu, X.; Zhu, X.; Li, J.; Ge, Z.; Chen, S. New insights into synergistic antimicrobial and antifouling cotton fabrics via dually finished with quaternary ammonium salt and zwitterionic sulfobetaine. *Chem. Eng. J.* **2018**, *336*, 123–132. [[CrossRef](#)]

16. Foksowicz-Flaczyk, J.; Walentowska, J.; Przybylak, M.; Maciejewski, H. Multifunctional durable properties of textile materials modified by biocidal agents in the sol-gel process. *Surf. Coat. Technol.* **2016**, *304*, 160–166. [[CrossRef](#)]
17. Przybylak, M.; Maciejewski, H.; Dudkiewicz, A.; Walentowska, J.; Foksowicz-Flaczyk, J. Development of multifunctional cotton fabrics using difunctional polysiloxanes. *Cellulose* **2018**, *25*, 1483–1497. [[CrossRef](#)]
18. Yazdankhah, S.P.; Scheie, A.A.; Høiby, E.A.; Lunestad, B.-T.; Heir, E.; Fotland, T.Ø.; Naterstad, K.; Kruse, H. Triclosan and Antimicrobial Resistance in Bacteria: An Overview. *Microb. Drug Resist.* **2006**, *12*, 83–90. [[CrossRef](#)]
19. Gu, J.; Yuan, L.; Zhang, Z.; Yang, X.; Luo, J.; Gui, Z.; Chen, S. Non-leaching bactericidal cotton fabrics with well-preserved physical properties, no skin irritation and no toxicity. *Cellulose* **2018**, *25*, 5415–5426. [[CrossRef](#)]
20. Alvarez-Risco, A.; Del-Aguila-Arcentales, S.; Delgado-Zegarra, J.; Yáñez, J.A.; Diaz-Risco, S. Doping in sports: Findings of the analytical test and its interpretation by the public. *Sport Sci. Health* **2019**, *15*, 255–257. [[CrossRef](#)]
21. Bermudez-Aguirre, D.; Yáñez, J.; Dunne, C.; Davies, N.; Barbosa-Cánovas, G. Study of strawberry flavored milk under pulsed electric field processing. *Food Res. Int.* **2010**, *43*, 2201–2207. [[CrossRef](#)]
22. Delgado-Zegarra, J.; Alvarez-Risco, A.; Cárdenas, C.; Donoso, M.; Moscoso, S.; Rojas Román, B.; Del-Aguila-Arcentales, S.; Davies, N.M.; Yáñez, J.A. Labeling of Genetically Modified (GM) Foods in Peru: Current Dogma and Insights of the Regulatory and Legal Statutes. *Int. J. Food Sci.* **2022**, *2022*, 3489785. [[CrossRef](#)]
23. Delgado-Zegarra, J.; Alvarez-Risco, A.; Yáñez, J.A. Uso indiscriminado de pesticidas y ausencia de control sanitario para el mercado interno en Perú. *Rev. Panam. Salud Pública* **2018**, *42*, e3. [[CrossRef](#)]
24. Mejia-Meza, E.I.; Yáñez, J.A.; Davies, N.M.; Clary, C.D. Dried Raspberries: Phytochemicals and Health Effects. In *Dried Fruits*; Wiley Online Library: Hoboken, NJ, USA, 2013; pp. 161–174.
25. Mejia-Meza, E.I.; Yanez, J.A.; Davies, N.M.; Rasco, B.; Younce, F.; Remsberg, C.M.; Clary, C. Improving nutritional value of dried blueberries (*Vaccinium corymbosum* L.) combining microwave-vacuum, hot-air drying and freeze-drying technologies. *Int. J. Food Eng.* **2008**, *4*, 1–6. [[CrossRef](#)]
26. Mejia-Meza, E.I.; Yanez, J.A.; Remsberg, C.M.; Takemoto, J.K.; Davies, N.M.; Rasco, B.; Clary, C. Effect of dehydration on raspberries: Polyphenol and anthocyanin retention, antioxidant capacity, and antiadipogenic activity. *J. Food Sci.* **2010**, *75*, H5–H12. [[CrossRef](#)]
27. Ramos-Escudero, D.F.; Condezo-Hoyos, L.A.; Ramos-Escudero, M.; Yanez, J.A. Design and assessment of the in vitro anti-oxidant capacity of a beverage composed of green tea (*Camellia sinensis* L.) and lemongrass (*Cymbopogon citratus* Stap). In *Handbook of Green Tea and Health Research*; McKinley, H., Jamieson, M., Eds.; Nova Science Publishers, Inc.: New York, NY, USA, 2009; pp. 81–101.
28. Ramos-Escudero, D.F.; Munoz, A.M.; Alvarado-Ortiz, C.; Yanez, J.A. Antocianinas, polifenoles, actividad anti-oxidante de sachapapa morada (*Dioscorea trifida* L.) y evaluación de lipoperoxidación en suero humano. *Rev. Soc. Quím. Perú* **2010**, *76*, 61–72.
29. Ramos-Escudero, F.; Muñoz, A.M.; Alvarado-Ortiz, C.; Alvarado, Á.; Yáñez, J.A. Purple corn (*Zea mays* L.) phenolic compounds profile and its assessment as an agent against oxidative stress in isolated mouse organs. *J. Med. Food* **2012**, *15*, 206–215. [[CrossRef](#)]
30. Ramos-Escudero, F.; Santos-Buelga, C.; Pérez-Alonso, J.J.; Yáñez, J.A.; Dueñas, M. HPLC-DAD-ESI/MS identification of anthocyanins in *Dioscorea trifida* L. yam tubers (purple sachapapa). *Eur. Food Res. Technol.* **2010**, *230*, 745–752. [[CrossRef](#)]
31. Ramos-Escudero, M.; Ramos-Escudero, D.F.; Remsberg, C.M.; Takemoto, J.K.; Davies, N.M.; Yanez, J.A. Identification of Polyphenols and Anti-Oxidant Capacity of *Piper aduncum* L. *Open Bioact. Compd. J.* **2008**, *1*, 18–21. [[CrossRef](#)]
32. Forrest, M.L.; Yanez, J.A.; Remsberg, C.M.; Ohgami, Y.; Kwon, G.S.; Davies, N.M. Paclitaxel prodrugs with sustained release and high solubility in poly(ethylene glycol)-b-poly(epsilon-caprolactone) micelle nanocarriers: Pharmacokinetic disposition, tolerability, and cytotoxicity. *Pharm. Res.* **2008**, *25*, 194–206. [[CrossRef](#)]
33. Yanez, J.A.; Forrest, M.L.; Ohgami, Y.; Kwon, G.S.; Davies, N.M. Pharmacometrics and delivery of novel nanoformulated PEG-b-poly(epsilon-caprolactone) micelles of rapamycin. *Cancer Chemother. Pharmacol.* **2008**, *61*, 133–144. [[CrossRef](#)] [[PubMed](#)]
34. Xiong, M.P.; Yanez, J.A.; Remsberg, C.M.; Ohgami, Y.; Kwon, G.S.; Davies, N.M.; Forrest, M.L. Formulation of a geldanamycin prodrug in mPEG-b-PCL micelles greatly enhances tolerability and pharmacokinetics in rats. *J. Control. Release* **2008**, *129*, 33–40. [[CrossRef](#)] [[PubMed](#)]
35. Xiong, M.P.; Yáñez, J.A.; Kwon, G.S.; Davies, N.M.; Forrest, M.L. A cremophor-free formulation for tanespimycin (17-AAG) using PEO-b-PDLLA micelles: Characterization and pharmacokinetics in rats. *J. Pharm. Sci.* **2009**, *98*, 1577–1586. [[CrossRef](#)] [[PubMed](#)]
36. Alrushaid, S.; Davies, N.M.; Anderson, J.E.; Le, T.; Yáñez, J.A.; Maayah, Z.H.; El-Kadi, A.O.S.; Rachid, O.; Sayre, C.L.; Löbenberg, R.; et al. Pharmaceutical characterization of myonovin, a novel skeletal muscle regenerator: In silico, in vitro and in vivo studies. *J. Pharm. Pharm. Sci.* **2018**, *21*, 1s–18s. [[CrossRef](#)]
37. Davies, N.M.; Takemoto, J.K.; Brocks, D.R.; Yáñez, J.A. Multiple peaking phenomena in pharmacokinetic disposition. *Clin. Pharmacokinet.* **2010**, *49*, 351–377. [[CrossRef](#)]
38. Davies, N.M.; Yáñez, J.A. *Flavonoid Pharmacokinetics: Methods of Analysis, Preclinical and Clinical Pharmacokinetics, Safety, and Toxicology*; Davies, N.M., Yáñez, J.A., Eds.; John Wiley & Sons: Hoboken, NJ, USA, 2012; p. 352.
39. Davies, N.M.; Yáñez, J.A. Front Matter. In *Flavonoid Pharmacokinetics: Methods of Analysis, Preclinical and Clinical Pharmacokinetics, Safety, and Toxicology*; Davies, N.M., Yáñez, J.A., Eds.; John Wiley & Sons: Hoboken, NJ, USA, 2012; pp. i–xv.
40. Louizos, C.; Yáñez, J.A.; Forrest, M.L.; Davies, N.M. Understanding the hysteresis loop conundrum in pharmacokinetic/pharmacodynamic relationships. *J. Pharm. Pharm. Sci.* **2014**, *17*, 34–91. [[CrossRef](#)]

41. Remsberg, C.M.; Yanez, J.A.; Ohgami, Y.; Vega-Villa, K.R.; Rimando, A.M.; Davies, N.M. Pharmacometrics of pterostilbene: Preclinical pharmacokinetics and metabolism, anticancer, antiinflammatory, antioxidant and analgesic activity. *Phytother. Res.* **2008**, *22*, 169–179. [[CrossRef](#)]
42. Remsberg, C.M.; Yanez, J.A.; Roupe, K.A.; Davies, N.M. High-performance liquid chromatographic analysis of pterostilbene in biological fluids using fluorescence detection. *J. Pharm. Biomed. Anal.* **2007**, *43*, 250–254. [[CrossRef](#)]
43. Roupe, K.; Remsberg, C.; Yanez, J.; Davies, N. Pharmacometrics of Stilbenes: Seguing Towards the Clinic. *Curr. Clin. Pharmacol.* **2006**, *1*, 81–101. [[CrossRef](#)]
44. Roupe, K.A.; Helms, G.L.; Halls, S.C.; Yanez, J.A.; Davies, N.M. Preparative enzymatic synthesis and HPLC analysis of rhapontigenin: Applications to metabolism, pharmacokinetics and anti-cancer studies. *J. Pharm. Pharm. Sci.* **2005**, *8*, 374–386.
45. Sayre, C.L.; Gerde, K.D.; Yáñez, J.A.; Davies, N.M. Clinical Pharmacokinetics of Flavonoids. In *Flavonoid Pharmacokinetics: Methods of Analysis, Preclinical and Clinical Pharmacokinetics, Safety, and Toxicology*; Davies, N.M., Yáñez, J.A., Eds.; John Wiley & Sons: Hoboken, NJ, USA, 2012; pp. 195–247.
46. Serve, K.M.; Yáñez, J.A.; Remsberg, C.M.; Davies, N.M.; Black, M.E. Development and validation of a rapid and sensitive HPLC method for the quantification of 5-fluorocytosine and its metabolites. *Biomed. Chromatogr.* **2010**, *24*, 556–561. [[CrossRef](#)]
47. Takemoto, J.K.; Remsberg, C.M.; Yanez, J.A.; Vega-Villa, K.R.; Davies, N.M. Stereospecific analysis of sakuranetin by high-performance liquid chromatography: Pharmacokinetic and botanical applications. *J. Chromatogr. B Anal. Technol. Biomed. Life Sci.* **2008**, *875*, 136–141. [[CrossRef](#)]
48. Vega-Villa, K.R.; Remsberg, C.M.; Ohgami, Y.; Yanez, J.A.; Takemoto, J.K.; Andrews, P.K.; Davies, N.M. Stereospecific high-performance liquid chromatography of taxifolin, applications in pharmacokinetics, and determination in tu fu ling (*Rhizoma smilacis glabrae*) and apple (*Malus × domestica*). *Biomed. Chromatogr.* **2009**, *23*, 638–646. [[CrossRef](#)]
49. Vega-Villa, K.R.; Remsberg, C.M.; Takemoto, J.K.; Ohgami, Y.; Yanez, J.A.; Andrews, P.K.; Davies, N.M. Stereospecific pharmacokinetics of racemic homoeriodictyol, isosakuranetin, and taxifolin in rats and their disposition in fruit. *Chirality* **2011**, *23*, 339–348. [[CrossRef](#)]
50. Vega-Villa, K.R.; Yanez, J.A.; Remsberg, C.M.; Ohgami, Y.; Davies, N.M. Stereospecific high-performance liquid chromatographic validation of homoeriodictyol in serum and Yerba Santa (*Eriodictyon glutinosum*). *J. Pharm. Biomed. Anal.* **2008**, *46*, 971–974. [[CrossRef](#)]
51. Yáñez, J.A.; Andrews, P.K.; Davies, N.M. Methods of analysis and separation of chiral flavonoids. *J. Chromatogr. B Anal. Technol. Biomed. Life Sci.* **2007**, *848*, 159–181. [[CrossRef](#)]
52. Yanez, J.A.; Brocks, D.R.; Forrest, M.L.; Davies, N.M. Pharmacokinetic Behaviors of Orally Administered Drugs. In *Oral Bioavailability: Basic Principles, Advanced Concepts, and Applications*; Hu, M., Li, X., Eds.; John Wiley & Sons, Inc.: Hoboken, NJ, USA, 2011; pp. 183–220.
53. Yáñez, J.A.; Chemuturi, N.V.; Womble, S.W.; Sayre, C.L.; Davies, N.M. Flavonoids and Drug Interactions. In *Flavonoid Pharmacokinetics: Methods of Analysis, Preclinical and Clinical Pharmacokinetics, Safety, and Toxicology*; Davies, N.M., Yáñez, J.A., Eds.; John Wiley & Sons: Hoboken, NJ, USA, 2012; pp. 281–319.
54. Yanez, J.A.; Davies, N.M. Stereospecific high-performance liquid chromatographic analysis of naringenin in urine. *J. Pharm. Biomed. Anal.* **2005**, *39*, 164–169. [[CrossRef](#)]
55. Yáñez, J.A.; Miranda, N.D.; Remsberg, C.M.; Ohgami, Y.; Davies, N.M. Stereospecific high-performance liquid chromatographic analysis of eriodictyol in urine. *J. Pharm. Biomed. Anal.* **2007**, *43*, 255–262. [[CrossRef](#)]
56. Yáñez, J.A.; Remsberg, C.M.; Sayre, C.L.; Forrest, M.L.; Davies, N.M. Flip-flop pharmacokinetics—delivering a reversal of disposition: Challenges and opportunities during drug development. *Ther. Deliv.* **2011**, *2*, 643–672. [[CrossRef](#)]
57. Yáñez, J.A.; Remsberg, C.M.; Takemoto, J.K.; Vega-Villa, K.R.; Andrews, P.K.; Sayre, C.L.; Martinez, S.E.; Davies, N.M. Polyphenols and Flavonoids: An Overview. In *Flavonoid Pharmacokinetics: Methods of Analysis, Preclinical and Clinical Pharmacokinetics, Safety, and Toxicology*; Davies, N.M., Yáñez, J.A., Eds.; John Wiley & Sons: Hoboken, NJ, USA, 2012; pp. 1–69.
58. Yáñez, J.A.; Sayre, C.L.; Davies, N.M. Preclinical Pharmacokinetics of Flavonoids. In *Flavonoid Pharmacokinetics: Methods of Analysis, Preclinical and Clinical Pharmacokinetics, Safety, and Toxicology*; Davies, N.M., Yáñez, J.A., Eds.; John Wiley & Sons: Hoboken, NJ, USA, 2012; pp. 161–193.
59. Yáñez, J.A.; Sayre, C.L.; Martinez, S.E.; Davies, N.M. Chiral Methods of Flavonoid Analysis. In *Flavonoid Pharmacokinetics: Methods of Analysis, Preclinical and Clinical Pharmacokinetics, Safety, and Toxicology*; Davies, N.M., Yáñez, J.A., Eds.; John Wiley & Sons: Hoboken, NJ, USA, 2012; pp. 117–159.
60. Yáñez, J.A.; Teng, X.W.; Roupe, K.A.; Davies, N.M. Stereospecific high-performance liquid chromatographic analysis of hesperetin in biological matrices. *J. Pharm. Biomed. Anal.* **2005**, *37*, 591–595. [[CrossRef](#)]
61. Yanez, J.A.; Wang, S.W.; Knemeyer, I.W.; Wirth, M.A.; Alton, K.B. Intestinal lymphatic transport for drug delivery. *Adv. Drug Deliv. Rev.* **2011**, *63*, 923–942. [[CrossRef](#)] [[PubMed](#)]
62. Chemuturi, N.; Yanez, J.A. The role of xenobiotic transporters in ophthalmic drug delivery. *J. Pharm. Pharm. Sci.* **2013**, *16*, 683–707. [[CrossRef](#)] [[PubMed](#)]
63. Vega-Villa, K.R.; Takemoto, J.K.; Yanez, J.A.; Remsberg, C.M.; Forrest, M.L.; Davies, N.M. Clinical toxicities of nanocarrier systems. *Adv. Drug Deliv. Rev.* **2008**, *60*, 929–938. [[CrossRef](#)] [[PubMed](#)]

64. Bonin, A.M.; Yáñez, J.A.; Fukuda, C.; Teng, X.W.; Dillon, C.T.; Hambley, T.W.; Lay, P.A.; Davies, N.M. Inhibition of experimental colorectal cancer and reduction in renal and gastrointestinal toxicities by copper-indomethacin in rats. *Cancer Chemother. Pharmacol.* **2010**, *66*, 755–764. [[CrossRef](#)]
65. Alrushaid, S.; Sayre, C.L.; Yáñez, J.A.; Forrest, M.L.; Senadheera, S.N.; Burczynski, F.J.; Löbenberg, R.; Davies, N.M. Pharmacokinetic and Toxicodynamic Characterization of a Novel Doxorubicin Derivative. *Pharmaceutics* **2017**, *9*, 35. [[CrossRef](#)]
66. Yanez, J.A.; Teng, X.W.; Roupe, K.A.; Davies, N.M. Alternative Methods for Assessing Experimental Colitis In Vivo and Ex Vivo. *J. Med. Sci.* **2006**, *6*, 356–365. [[CrossRef](#)]
67. Chung, S.A.; Olivera, S.; Rojas Román, B.; Alanoca, E.; Moscoso, S.; Limpías Terceros, B.; Alvarez-Risco, A.; Yáñez, J.A. Temáticas de la producción científica de la Revista Cubana de Farmacia indizada en Scopus (1967–2020). *Rev. Cuba. De Farm.* **2021**, *54*, 1–46.
68. Hebeish, A.; Abdel-Mohdy, F.A.; Fouda, M.M.G.; Elsaid, Z.; Essam, S.; Tammam, G.H.; Drees, E.A. Green synthesis of easy care and antimicrobial cotton fabrics. *Carbohydr. Polym.* **2011**, *86*, 1684–1691. [[CrossRef](#)]
69. Ashayer-Soltani, R.; Hunt, C.; Thomas, O. Fabrication of highly conductive stretchable textile with silver nanoparticles. *Text. Res. J.* **2015**, *86*, 1041–1049. [[CrossRef](#)]
70. Gorjanc, M.; Kovač, F.; Gorenšek, M. The influence of vat dyeing on the adsorption of synthesized colloidal silver onto cotton fabrics. *Text. Res. J.* **2011**, *82*, 62–69. [[CrossRef](#)]
71. Ravindra, S.; Murali Mohan, Y.; Narayana Reddy, N.; Mohana Raju, K. Fabrication of antibacterial cotton fibres loaded with silver nanoparticles via “Green Approach”. *Colloids Surf. A: Physicochem. Eng. Asp.* **2010**, *367*, 31–40. [[CrossRef](#)]
72. Radetić, M. Functionalization of textile materials with silver nanoparticles. *J. Mater. Sci.* **2013**, *48*, 95–107. [[CrossRef](#)]
73. Said, M.M.; Rehan, M.; El-Sheikh, S.M.; Zahran, M.K.; Abdel-Aziz, M.S.; Bechelany, M.; Barhoum, A. Multifunctional Hydroxyapatite/Silver Nanoparticles/Cotton Gauze for Antimicrobial and Biomedical Applications. *Nanomaterials* **2021**, *11*, 429. [[CrossRef](#)]
74. Gao, Y.-N.; Wang, Y.; Yue, T.-N.; Weng, Y.-X.; Wang, M. Multifunctional cotton non-woven fabrics coated with silver nanoparticles and polymers for antibacterial, superhydrophobic and high performance microwave shielding. *J. Colloid Interface Sci.* **2021**, *582*, 112–123. [[CrossRef](#)]
75. Maghima, M.; Alharbi, S.A. Green synthesis of silver nanoparticles from *Curcuma longa* L. and coating on the cotton fabrics for antimicrobial applications and wound healing activity. *J. Photochem. Photobiol. B Biol.* **2020**, *204*, 111806. [[CrossRef](#)]
76. Vigneshwaran, N.; Kathe, A.A.; Varadarajan, P.V.; Nachane, R.P.; Balasubramanya, R.H. Functional Finishing of Cotton Fabrics Using Silver Nanoparticles. *J. Nanosci. Nanotechnol.* **2007**, *7*, 1893–1897. [[CrossRef](#)]
77. Liu, H.-L.; Dai, S.A.; Fu, K.-Y.; Hsu, S.-H. Antibacterial properties of silver nanoparticles in three different sizes and their nanocomposites with a new waterborne polyurethane. *Int. J. Nanomed.* **2010**, *5*, 1017–1028.
78. Perera, S.; Bhushan, B.; Bandara, R.; Rajapakse, G.; Rajapakse, S.; Bandara, C. Morphological, antimicrobial, durability, and physical properties of untreated and treated textiles using silver-nanoparticles. *Colloids Surf. A Physicochem. Eng. Asp.* **2013**, *436*, 975–989. [[CrossRef](#)]
79. Wu, Y.; Yang, Y.; Zhang, Z.; Wang, Z.; Zhao, Y.; Sun, L. Fabrication of cotton fabrics with durable antibacterial activities finishing by Ag nanoparticles. *Text. Res. J.* **2018**, *89*, 867–880. [[CrossRef](#)]
80. Wu, M.; Guo, H.; Liu, L.; Liu, Y.; Xie, L. Size-dependent cellular uptake and localization profiles of silver nanoparticles. *Int. J. Nanomed.* **2019**, *14*, 4247–4259. [[CrossRef](#)]
81. Skomrokhova, E.A.; Sankova, T.P.; Orlov, I.A.; Savelev, A.N.; Magazenkova, D.N.; Pliss, M.G.; Skvortsov, A.N.; Sosnin, I.M.; Kirilenko, D.A.; Grishchuk, I.V.; et al. Size-Dependent Bioactivity of Silver Nanoparticles: Antibacterial Properties, Influence on Copper Status in Mice, and Whole-Body Turnover. *Nanotechnol. Sci. Appl.* **2020**, *13*, 137–157. [[CrossRef](#)]
82. Emam, H.E.; Saleh, N.H.; Nagy, K.S.; Zahran, M.K. Functionalization of medical cotton by direct incorporation of silver nanoparticles. *Int. J. Biol. Macromol.* **2015**, *78*, 249–256. [[CrossRef](#)]
83. Vanaja, M.; Gnanajobitha, G.; Paulkumar, K.; Rajeshkumar, S.; Malarkodi, C.; Annadurai, G. Phytosynthesis of silver nanoparticles by *Cissus quadrangularis*: Influence of physicochemical factors. *J. Nanostructure Chem.* **2013**, *3*, 17. [[CrossRef](#)]
84. Rivas-Cáceres, R.R.; Luis Stephano-Hornedo, J.; Lugo, J.; Vaca, R.; Del Aguila, P.; Yáñez-Ocampo, G.; Mora-Herrera, M.E.; Camacho Díaz, L.M.; Cipriano-Salazar, M.; Alaba, P.A. Bactericidal effect of silver nanoparticles against propagation of *Clavibacter michiganensis* infection in *Lycopersicon esculentum* Mill. *Microb. Pathog.* **2018**, *115*, 358–362. [[CrossRef](#)]
85. Hambardzumyan, S.; Sahakyan, N.; Petrosyan, M.; Nasim, M.J.; Jacob, C.; Trchounian, A. *Origanum vulgare* L. extract-mediated synthesis of silver nanoparticles, their characterization and antibacterial activities. *AMB Express* **2020**, *10*, 162. [[CrossRef](#)]
86. El-Rafie, M.H.; Ahmed, H.B.; Zahran, M.K. Characterization of nanosilver coated cotton fabrics and evaluation of its antibacterial efficacy. *Carbohydr. Polym.* **2014**, *107*, 174–181. [[CrossRef](#)]
87. Escárcega-González, C.E.; Garza-Cervantes, J.A.; Vázquez-Rodríguez, A.; Morones-Ramírez, J.R. Bacterial Exopolysaccharides as Reducing and/or Stabilizing Agents during Synthesis of Metal Nanoparticles with Biomedical Applications. *Int. J. Polym. Sci.* **2018**, *2018*, 7045852. [[CrossRef](#)]
88. Bao, Y.; Feng, C.; Wang, C.; Ma, J.; Tian, C. Hygienic, antibacterial, UV-shielding performance of polyacrylate/ZnO composite coatings on a leather matrix. *Colloids Surf. A: Physicochem. Eng. Asp.* **2017**, *518*, 232–240. [[CrossRef](#)]
89. Yu, Z.; Liu, J.; He, H.; Wang, Y.; Zhao, Y.; Lu, Q.; Qin, Y.; Ke, Y.; Peng, Y. Green synthesis of silver nanoparticles with black rice (*Oryza sativa* L.) extract endowing carboxymethyl chitosan modified cotton with high anti-microbial and durable properties. *Cellulose* **2021**, *28*, 1827–1842. [[CrossRef](#)]

90. Ibrahim, N.A.; Amr, A.; Eid, B.M. Multipurpose Treatment of Cellulose-Containing Fabrics to Impart Durable Antibacterial and Repellent Properties. *Fibers Polym.* **2020**, *21*, 513–521. [[CrossRef](#)]
91. El-Naggar, M.E.; Abdelgawad, A.M.; Elsherbiny, D.A.; El-shazly, W.A.; Ghazanfari, S.; Abdel-Aziz, M.S.; Abd-Elmoneam, Y.K. Bioactive Wound Dressing Gauze Loaded with Silver Nanoparticles Mediated by Acacia Gum. *J. Clust. Sci.* **2020**, *31*, 1349–1362. [[CrossRef](#)]
92. El-Naggar, M.E.; Shaarawy, S.; Hebeish, A.A. Bactericidal finishing of loomstate, scoured and bleached cotton fibres via sustainable in-situ synthesis of silver nanoparticles. *Int. J. Biol. Macromol.* **2018**, *106*, 1192–1202. [[CrossRef](#)]
93. Abdelgawad, A.M.; El-Naggar, M.E.; Elsherbiny, D.A.; Ali, S.; Abdel-Aziz, M.S.; Abdel-Monem, Y.K. Antibacterial carrageenan/cellulose nanocrystal system loaded with silver nanoparticles, prepared via solid-state technique. *J. Environ. Chem. Eng.* **2020**, *8*, 104276. [[CrossRef](#)]
94. Hassabo, A.G.; El-Naggar, M.E.; Mohamed, A.L.; Hebeish, A.A. Development of multifunctional modified cotton fabric with tri-component nanoparticles of silver, copper and zinc oxide. *Carbohydr. Polym.* **2019**, *210*, 144–156. [[CrossRef](#)]
95. Ignatious, V.; Raveendran, N.; Prabhakaran, A.; Tanjore Puli, Y.; Chakkooth, V.; Deb, B. MWCNT/Thienothiophene based All-Organic thermoelectric composites: Enhanced performance by realigning of the Fermi level through doping. *Chem. Eng. J.* **2021**, *409*, 128294. [[CrossRef](#)]
96. Ahmed, H.; Khattab, T.A.; Mashaly, H.M.; El-Halwagy, A.A.; Rehan, M. Plasma activation toward multi-stimuli responsive cotton fabric via in situ development of polyaniline derivatives and silver nanoparticles. *Cellulose* **2020**, *27*, 2913–2926. [[CrossRef](#)]
97. Katouah, H.; El-Metwaly, N.M. Plasma treatment toward electrically conductive and superhydrophobic cotton fibers by in situ preparation of polypyrrole and silver nanoparticles. *React. Funct. Polym.* **2021**, *159*, 104810. [[CrossRef](#)]
98. El-Naggar, M.E.; Khattab, T.A.; Abdelrahman, M.S.; Aldalbahi, A.; Hatshan, M.R. Development of antimicrobial, UV blocked and photocatalytic self-cleanable cotton fibers decorated with silver nanoparticles using silver carbamate and plasma activation. *Cellulose* **2021**, *28*, 1105–1121. [[CrossRef](#)]
99. Zea Álvarez, J.L.; Talavera Núñez, M.E.; Arenas Chávez, C.; Pacheco Salazar, D.; Osorio Anaya, A.M.; Vera Gonzales, C. Obtención y caracterización del nanocomposito: Nanopartículas de plata y carboximetilquitosano (NPsAg-CMQ). *Rev. Soc. Química Perú* **2019**, *85*, 14–24. [[CrossRef](#)]
100. Gressier, P.; De Smet, D.; Behary, N.; Campagne, C.; Vanneste, M. Antibacterial polyester fabrics via diffusion process using active bio-based agents from essential oils. *Ind. Crops Prod.* **2019**, *136*, 11–20. [[CrossRef](#)]
101. Balandin, G.V.; Suvorov, O.A.; Shaburova, L.N.; Podkopayev, D.O.; Frolova, Y.V.; Ermolaeva, G.A. The study of the antimicrobial activity of colloidal solutions of silver nanoparticles prepared using food stabilizers. *J. Food Sci. Technol.* **2015**, *52*, 3881–3886. [[CrossRef](#)]
102. Balamurugan, M.; Saravanan, S.; Soga, T. Coating of green-synthesized silver nanoparticles on cotton fabric. *J. Coat. Technol. Res.* **2017**, *14*, 735–745. [[CrossRef](#)]
103. Gao, D.; Li, Y.; Lyu, B.; Lyu, L.; Chen, S.; Ma, J. Construction of durable antibacterial and anti-mildew cotton fabric based on P(DMDAAC-AGE)/Ag/ZnO composites. *Carbohydr. Polym.* **2019**, *204*, 161–169. [[CrossRef](#)]
104. Paszkiewicz, M.; Gołabiewska, A.; Rajski, Ł.; Kowal, E.; Sajdak, A.; Zaleska-Medynska, A. Synthesis and characterization of monometallic (Ag, Cu) and bimetallic Ag-Cu particles for antibacterial and antifungal applications. *J. Nanomater.* **2016**, *2016*, 6. [[CrossRef](#)]
105. Hebeish, A.; El-Naggar, M.E.; Fouda, M.M.G.; Ramadan, M.A.; Al-Deyab, S.S.; El-Rafie, M.H. Highly effective antibacterial textiles containing green synthesized silver nanoparticles. *Carbohydr. Polym.* **2011**, *86*, 936–940. [[CrossRef](#)]
106. Raza, Z.A.; Rehman, A.; Mohsin, M.; Bajwa, S.Z.; Anwar, F.; Naeem, A.; Ahmad, N. Development of antibacterial cellulosic fabric via clean impregnation of silver nanoparticles. *J. Clean. Prod.* **2015**, *101*, 377–386. [[CrossRef](#)]
107. Sathishkumar, M.; Sneha, K.; Won, S.W.; Cho, C.W.; Kim, S.; Yun, Y.S. Cinnamon zeylanicum bark extract and powder mediated green synthesis of nano-crystalline silver particles and its bactericidal activity. *Colloids Surf. B Biointerfaces* **2009**, *73*, 332–338. [[CrossRef](#)]
108. Yang, N.; Li, W.-H. Mango peel extract mediated novel route for synthesis of silver nanoparticles and antibacterial application of silver nanoparticles loaded onto non-woven fabrics. *Ind. Crops Prod.* **2013**, *48*, 81–88. [[CrossRef](#)]
109. Hebeish, A.; El-Shafei, A.; Sharaf, S.; Zaghloul, S. In situ formation of silver nanoparticles for multifunctional cotton containing cyclodextrin. *Carbohydr. Polym.* **2014**, *103*, 442–447. [[CrossRef](#)]
110. Yu, D.; Tian, W.; Sun, B.; Li, Y.; Wang, W.; Tian, W. Preparation of silver-plated wool fabric with antibacterial and anti-mould properties. *Mater. Lett.* **2015**, *151*, 1–4. [[CrossRef](#)]